



Enhancement of iodinin solubility by encapsulation into cyclodextrin nanoparticles

Anthony Prandina, Lars Herfindal, Sylvie Radix, Pål Rongved, Stein O. Døskeland, Marc Le Borgne & Florent Perret

To cite this article: Anthony Prandina, Lars Herfindal, Sylvie Radix, Pål Rongved, Stein O. Døskeland, Marc Le Borgne & Florent Perret (2018) Enhancement of iodinin solubility by encapsulation into cyclodextrin nanoparticles, Journal of Enzyme Inhibition and Medicinal Chemistry, 33:1, 370-375, DOI: [10.1080/14756366.2017.1421638](https://doi.org/10.1080/14756366.2017.1421638)

To link to this article: <https://doi.org/10.1080/14756366.2017.1421638>



© 2018 The Author(s). Published by Informa UK Limited, trading as Taylor & Francis Group.



View supplementary material [↗](#)



Published online: 16 Jan 2018.



Submit your article to this journal [↗](#)



Article views: 144



View related articles [↗](#)








View Crossmark data [↗](#)

RESEARCH ARTICLE



Enhancement of iodinin solubility by encapsulation into cyclodextrin nanoparticles

Anthony Prandina^{a,b}, Lars Herfindal^c, Sylvie Radix^a , Pål Rongved^b , Stein O. Døskeland^d ,
Marc Le Borgne^a  and Florent Perret^e 

^aUniversité de Lyon, Université Claude Bernard Lyon 1, Faculté de Pharmacie – ISPB, EA 4446 Bioactive Molecules and Medicinal Chemistry, SFR Santé Lyon-Est CNRS UMS3453 – INSERM U57, Lyon Cedex, France; ^bDepartment of Pharmaceutical Chemistry, School of Pharmacy, University of Oslo, Oslo, Norway; ^cCentre for Pharmacy, Department of Clinical Science, University of Bergen, Bergen, Norway; ^dDepartment of Biomedicine, University of Bergen, Bergen, Norway; ^eUniversité de Lyon, Université Claude Bernard Lyon 1, Institut de Chimie et Biochimie Moléculaires et Supramoléculaires, UMR 5246 CNRS – CPE Lyon – INSA, Villeurbanne Cedex, France

ABSTRACT

Phenazine is known to regroup planar nitrogen-containing heterocyclic compounds. It was used here to enhance the bioavailability of the biologically important compound iodinin, which is near insoluble in aqueous solutions. Its water solubility has led to the development of new formulations using diverse amphiphilic α -cyclodextrins (CDs). With the per-[6-desoxy-6-(3-perfluorohexylpropanethio)-2,3-di-O-methyl]- α -CD, we succeeded to get iodinin-loaded nanoformulations with good parameters such as a size of 97.9 nm, 62% encapsulation efficiency and efficient control release. The study presents an interesting alternative to optimizing the water solubility of iodinin by chemical modifications of iodinin.

ARTICLE HISTORY

Received 29 October 2017
Revised 21 December 2017
Accepted 22 December 2017

KEYWORDS

Iodinin; solubility;
amphiphilic α -cyclodextrin;
nanoparticles; encapsulation

Introduction


Phenazine is a dibenzo annulated pyrazine present in many natural products^{1–3} and has become the parent substance of many synthetic bioactive molecules^{4–6}. The broad spectrum of biological activities of phenazine explains the success of research programs exploiting this scaffold. The most striking examples are the targeting of antibiotic-tolerant bacterial biofilms and *Mycobacterium tuberculosis* by halogenated phenazines⁷. Other derivatives such as endophenazine G showed activity against community-associated methicillin-resistant *Staphylococcus aureus*⁸. Phenazine-1-carboxylic acid derivatives exhibit fungicidal activities⁹ and finally numerous phenazines were developed as anti-cancer agents¹⁰, for example, the novel pyrano[3,2-*a*]phenazine derivatives demonstrated anti-proliferative activity against the HepG2 cancer cell line¹¹.

Iodinin (Figure 1) was first discovered in 1939¹² within *Chromobacterium iodinum* bacterial cultures. In 1943, McIlwain demonstrated its anti-streptococcal action¹³. For the last 75 years, iodinin has been isolated from diverse soil bacteria (e.g. *Brevibacterium iodinum*¹⁴, *Pseudomonas phenazinum*¹⁵, *Nocardiopsis dassonvillei*¹⁶, and *Acidithiobacillus ferrooxidans*¹⁷), or marine bacteria (e.g. *Actinomadura* sp.¹⁸, *Streptosporangium* sp.¹⁹). Recently, recombinant *Pseudomonas* strains were used successfully to propose an alternative for the biosynthesis of natural phenazines²⁰. Iodinin displays other biological activities, including antimicrobial and cytotoxic properties^{21,22}. Actually, it is worth noting that iodinin showed remarkable selective toxicity to acute myeloid leukaemia (AML) and acute promyelocytic leukaemia (APL) cells, with various proposed mechanisms of action suggested such as DNA intercalation and activation of apoptotic signalling proteins (e.g. caspase-3)¹⁹.

The first total synthesis of iodinin was recently described by Viktorsson et al.²¹. The physical chemical properties of iodinin can be summarised as follows: it is a dark red solid, stable in acidic solution, unstable in alkali. Iodinin's solubility in different solvent can be summarised as follows: it is soluble in benzene, toluene, xylene, carbon disulphide, chloroform, ethyl acetate, THF, concentrated sulfuric acid, glacial acetic acid and sodium hydroxide. It is also slightly soluble in hot alcohol. In parallel, iodinin is practically insoluble in cold alcohol, ether, acetic acid, petroleum ether, or amyl alcohol²¹. Finally, iodinin is absolutely insoluble in water. In addition, various assays²¹ showed that iodinin solutions turned (i) pink when it was solubilised in most solvents; (ii) purple in chloroform with formation of crystals with a coppery sheen; (iii) red in glacial acetic acid and (iv) brilliant blue in sodium hydroxide with the deposition of green crystals from unstable sodium derivatives. It thus appears that iodinin is a bioactive molecule, which is difficult to manage in most biological investigations. To overcome this issue, we envisaged to complex iodinin with cyclodextrins (CDs) to increase aqueous solubility and bioavailability.

Amphiphilic CD derivatives have been available for decades^{23,24} mainly to overcome problems of native CDs that limit their applications in pharmaceutical fields. Indeed, since dissociation takes place too readily upon dilution, untimely release may take place during administration to the patient, so that inclusion complexes inside simple water-soluble CD appear ineffective for drug delivery applications. In fact, the use of amphiphilic CDs (i) enhances the interaction with biological membranes, (ii) modifies or enhances interaction of CDs with hydrophobic drugs, and (iii) allows self-assembly of CDs, forming nanosized carriers and encapsulating drugs^{25,26}. Polycationic CD nanoparticles containing siRNA have

CONTACT Florent Perret  florent.perret@univ-lyon1.fr  ICBMS-Equipe CSAP, Université Lyon 1, Bâtiment Raulin, 43 Bd du 11 novembre 1918, F-69622 Villeurbanne Cedex, France; Marc Le Borgne  marc.le-borgne@univ-lyon1.fr  Université Claude Bernard Lyon 1, Faculté de Pharmacie – ISPB, EA 4446 Bioactive Molecules and Medicinal Chemistry, 8 avenue Rockefeller, F-69373, Lyon Cedex 8, France

 Supplemental data for this article can be accessed [here](#).

© 2018 The Author(s). Published by Informa UK Limited, trading as Taylor & Francis Group.

This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.




Figure 1. Structure of iodinin (1,6-dihydroxyphenazine 5,10-dioxide).

been recently used for the delivery of siRNA to the glomerular mesangium²⁷.

Our group has published several studies demonstrating synthesis of amphiphilic CDs which were able self-assemble to form stable nanoparticles. Most of our amphiphilic derivatives have been prepared by modifying their primary face with hydrocarbon or perfluorocarbon lipophilic chains^{28–31}. As demonstrated previously for a hydrophobic indeno[1,2-*b*]indole analog³², not only could these nanoparticles encapsulate this CK2 inhibitor but also released it in a controlled manner.

This study deals with the formation and anti-leukemic activity of iodinin-loaded nanoparticles made from amphiphilic α -CDs. Encapsulation efficiency and release profiles are reported and show the beneficial effect of the fluorinated amphiphilic α -CD derivatives. The non-toxicity of these derivatives on red blood cells confirmed their potential use for *in vivo* assays.

Experimental

General

All chemical were purchased from Sigma-Aldrich, La Jolla, CA, USA and were used without further purification. Native α -cyclodextrin was generously provided by Roquette Frères (Lestrem, France). Amphiphilic fluorinated α -CDs and their hydrocarbon analogues (Figure 2) were synthesised as previously described^{28,31}. Briefly, after the selective protection of the primary hydroxyl groups with tertbutyldimethylsilyl groups, all the secondary hydroxyl groups were methylated using sodium hydride and methyl iodide. Removal of the tertbutyldimethylsilyl groups was performed with tetrabutylammonium fluoride in THF and introduction of the methanesulfonyl groups with methanesulfonyl chloride. Finally, the hydrophobic chains (fluorinated or hydrocarbonated) were introduced by nucleophilic substitution of the leaving groups by the thiolate derivate, generated *in situ* by the basic hydrolysis of the 3-perfluoroalkylpropane (or alkyl) isothiuronium salts using cesium carbonate. The structures and purities were confirmed using ¹H and ¹³C NMR and mass spectroscopy analysis.

Iodinin was isolated from batch cultures of the bacterium *Streptosporangium* sp. The bacterial mass culturing conditions, as well as the protocol for DMSO-extraction, subsequent HPLC-purification and identification of iodinin by MS and NMR were carried out as previously described^{19,22}.

Dynamic light scattering measures were performed using a Zetasizer Nano ZSP instrument from Malvern Instruments, Malvern, UK.

Preparation of nanoparticles by the highly loaded method

The iodinin loaded nanoparticles based α -CD were prepared by the nanoprecipitation technique, using a 0.8×10^{-4} M solution of preformed (1:1) iodinin: α -CD complexes overloaded with an additional amount of iodinin in the THF phase. The total concentration of iodinin was 1.6×10^{-4} M (iodinin/CD ratio = 2).

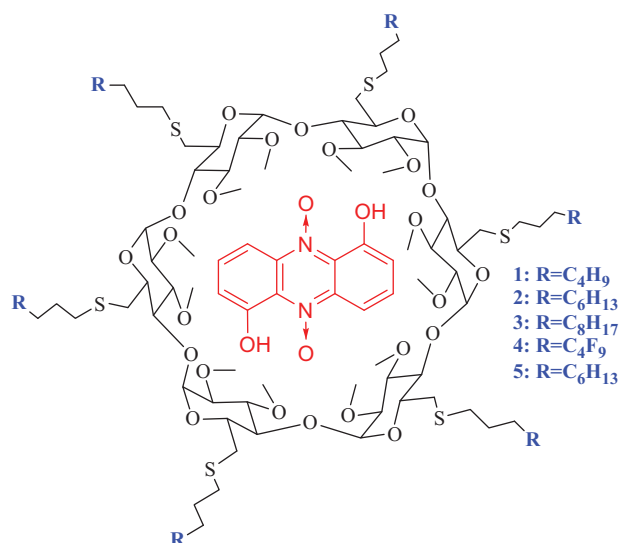


Figure 2. Structure of inclusion complex of iodinin (red) in amphiphilic alkyl (1–3) or perfluoroalkyl (4,5) α -cyclodextrins.

The relevant solution of the preformed complex in THF (25 ml, 1 day stirring) was poured drop-wise into deionised water (50 ml) while stirring. A slightly turbid emulsion of nanospheres spontaneously formed. Solvent and a part of water were evaporated under reduced pressure and the total volume adjusted to 50 ml with water.

Particle size measurements

The mean particle size (diameter, nm) and the polydispersity index (PDI) of nanospheres were measured by dynamic light scattering using a NanoZS instrument, which analyses the fluctuations of scattered light intensity generated by diffusion of the particles in a diluted suspension (dynamic light scattering data are shown in Figures S1–S5 and Zeta potentials of empty and loaded nanoparticle dispersions are presented in Figures S6–S10). The measurements were carried out at 25 °C. Experiments were performed in triplicate.

Determination of the encapsulation efficiency

For measuring the loading efficiency, after the formation of nanoparticle suspensions by the highly loaded method, non-encapsulated iodinin in the nanoparticle dispersions was separated by centrifugation at 50,000 rpm for 1 h in order to settle down the loaded nanoparticles. The supernatant was removed. The precipitate was then lyophilised overnight, and the resulting powder containing the loaded nanoparticles was dissolved in a known amount of THF in order to obtain a clear solution. The absorbance of supernatant and THF solutions was analysed using an UV spectrophotometer at 289 nm to calculate the encapsulated drug quantity. Loading capacity was expressed in terms of associated drug percentage:

$$\text{Associated drug (\%)} = \frac{[\text{determined iodinin quantity (mol)}]}{[\text{initial iodinin quantity (mol)}]} \times 100$$

In vitro release studies

The suspensions of nanoparticles made from C₆H₁₃, C₈H₁₇ and C₆F₁₃ derivatives loaded with iodinin (1 ml of a 0.8×10^{-4} M

solution) were introduced into a dialysis tube (cutoff 5000 Da) at 25 °C. This tube was then placed in a higher volume (20 ml) of phosphate buffered solution (pH 7.4) for a period of time. Same experiments have been done with non-encapsulated iodinin by using 1 ml of a 0.8×10^{-4} M iodinin THF/water solution. Aliquots of 1 ml of the buffered solution were removed at different time intervals to calculate the proportion of released and encapsulated molecules by UV spectrometry at 289 nm.

Cytotoxicity studies

The formulations were tested on the Brown Norwegian myeloid leukaemia (BNML) rat-derived AML cell line IPC-81³³. The cells were cultured in Dulbecco's Modified Eagles Medium (DMEM; Sigma, La Jolla, CA, USA) enriched with 10% horse serum (Invitrogen, Carlsbad, CA, USA), and added 100 IU/L penicillin and 100 mg/L streptomycin (both from Cambrex, Verviers, Belgium), and cultured in a humidified atmosphere (37 °C, 5% CO₂). For cytotoxicity testing, the cells were seeded in 96 well tissue culture plates at 150,000 cells/mL. The cells were exposed to various concentrations of empty or iodinin-loaded nanoparticles for 24 h and then fixed in 2% buffered formaldehyde (pH 7.4) with the DNA-specific dye Hoechst 33342 (Polysciences Inc., Eppelheim, Germany) and scored for apoptosis as previously described^{34,35}.

Results and discussion

α -CD nanoparticles

It has been reported that the highly loaded method was the most efficient for encapsulating hydrophobic compounds inside amphiphilic CD-based nanoparticles³⁰. Since iodinin is hydrophobic, this

Table 1. Characteristics of loaded nanoparticles made from amphiphilic α -cyclodextrins.

Derivative	Side chain	Nanoparticle size (nm) loaded/empty	Polydispersity index (PDI) loaded/empty	Associated drug (%)
1	C ₄ H ₉	159.3/162.3	0.07/0.04	40
2	C ₆ H ₁₃	117.0/126.3	0.10/0.13	54
3	C ₈ H ₁₇	104.1/105.8	0.11/0.05	58
4	C ₄ F ₉	109.7/120.7	0.02/0.25	36
5	C ₆ F ₁₃	097.9/90.6	0.08/0.10	62

method was chosen for its encapsulation, using THF as co-solvent which allowed the solubilisation of both iodinin and amphiphilic CD derivatives.

As shown in Table 1 and Figure 3, the different nanoparticles had similar sizes, ranging from 97.9 nm to 156.2 nm. Comparing 1/4 and 2/5, it was noticed that, for the same hydrophobic chain length, perfluorinated nanoparticles gave lower diameters than the hydrogenated ones. In fact, the specific properties of fluorinated chains allowed for a more compact organisation of the hydrophobic chains inside the nanoparticles. Furthermore, for the same series (hydrogenated or fluorinated), it was an inverse relationship between the chain length and the size of the nanoparticle. It is also worth noting that empty nanoparticles had similar sizes as the loaded nanoparticles. All these data were found to match findings previously described in literature^{31,32}.

The experiments, run in triplicate, yielded particles with narrow size distribution (PDI <0.2) demonstrating high homogeneity of the nanoparticle suspensions.

The loading efficiency of iodinin in these various nanoparticles ranged from 36% to 62% for C₄H₉ and C₆F₁₃, respectively. Nevertheless, unlike what has been observed previously for acyclovir, nanospheres made from fluorinated α -CDs did not have significant impact on the encapsulation rate. The main differences were observed by varying the chain length (40%, 54% and 58% for C₄H₉, C₆H₁₃ and C₈H₁₇, respectively), suggesting that C₈F₁₇ would be slightly more efficient for encapsulation of iodinin.

The controlled release studies was performed on suspensions having at least 50% encapsulated iodinin (i.e. C₆H₁₃, C₈H₁₇ and C₆F₁₃) in comparison with the profile obtained without any nanoparticles (a 0.8×10^{-4} M iodinin solution alone in THF/water solution). As shown in Figure 4, in the absence of nanospheres, the concentration equilibrium between the outside and inside compartments of the dialysis tube was obtained in less than 40 min.

The release profiles showed the positive effect of the nanoparticles on the controlled release (Figure 4). Iodinin release from highly loaded nanospheres reached completion within more than one hour for hydrocarbon amphiphilic α -CDs and between 2.5 and 3 h for the fluorinated nanospheres. After 1 h, 72% of the encapsulated iodinin were released from the C₆H₁₃ nanospheres versus only 30% from the fluorinated analogue. It can be explained by the fact that fluorinated chains enhance intermolecular interactions inside the supramolecular assemblies compared to hydrogenated analogues, leading to more stable nanoparticles. These

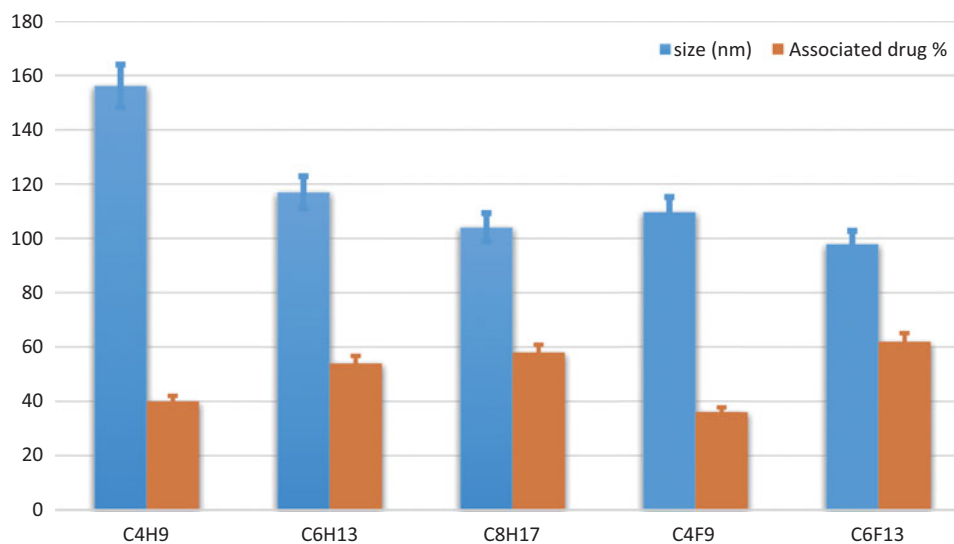


Figure 3. Sizes (in nm) of loaded nanoparticles and percentages of encapsulated iodinin for each derivative.

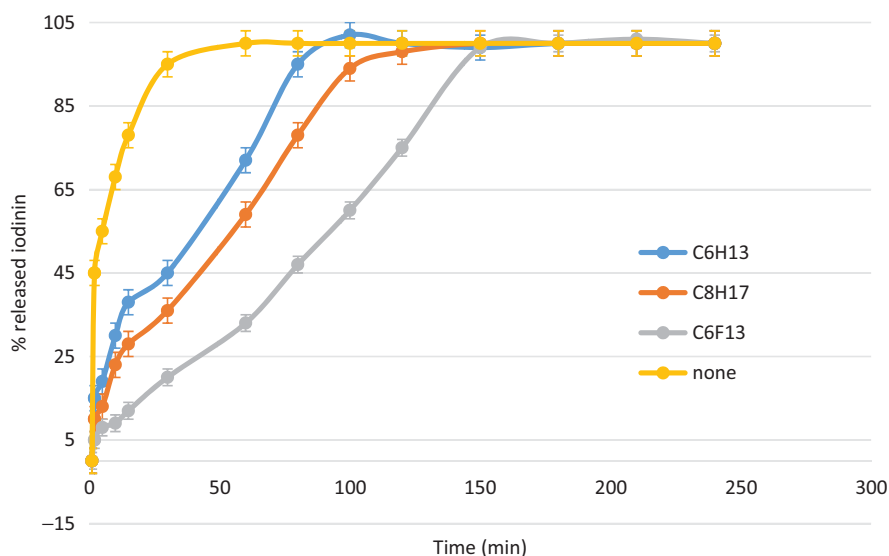


Figure 4. Release profiles of iodinin in phosphate buffered aqueous solution (pH 7.4).

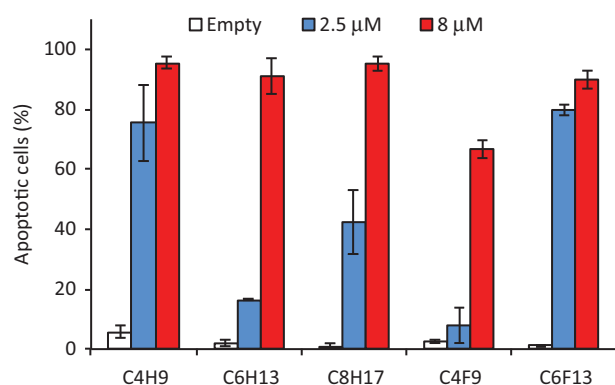


Figure 5. Cytotoxicity of iodinin-loaded amphiphilic CD-nanospheres towards the AML cell line IPC-81. The cells were incubated with the different formulations for 24 h before assessment of cell death. The data are average of two separate experiments. The error bars indicate the two measurements.

observations confirm previous studies which have showed that nanoparticles based on fluorinated compounds delayed acyclovir release, showing their potential for applications to drug delivery³⁰.

A particular point needs to be added about the toxicity of amphiphilic α -CDs. A recent study³⁶ related a study of cytotoxicity on red blood cells. The results confirmed the potential of amphiphilic α -CDs to formulate bioactive molecules and then to be used for *in vivo* assays. We tested empty or iodinin-loaded fluorinated amphiphilic CD nanospheres for ability to induce cell death in the BNML-derived rat AML cell line IPC-81. This cell line produces AML with typical signs of the disease in xenograft mouse models, and responds to the benchmark AML drug daunorubicin *in vitro* and *in vivo*³⁷. We found no toxicity towards the IPC-81 cells with any of the empty nanoparticles (Figure 5). Iodinin-loaded nanoparticles, however, efficiently induced IPC-81 AML cell death within 24 h (Figure 5). From the different CD-compositions tested, we found that the C₄H₉ and C₆F₁₃ were the most potent formulations, whereas C₆H₁₃ and C₄F₉ were the least potent formulations. This is opposite to what was seen in the release studies, which showed that C₆H₁₃ released their cargo at a faster rate than C₆F₁₃ (Figure 4). This suggests that internalisation of the nanoparticles indeed play a role in the cytotoxic effect of the amphiphilic α -CD nanospheres. Although the efficacy of the nanospheres appeared lower than the original compound^{19,21}, the

encapsulation of iodinin is expected to lower toxic effects on non-target cells, thus increasing the therapeutic index for this potent AML-selective compound.

Conclusions

This study describes the successful preparation of iodinin-loaded nanoparticles. The results indicate that nanoencapsulation of iodinin in α -CDs by the highly loaded method is possible, without any additional surface-active agent. With per-[6-desoxy-6-(3-perfluorohexylpropanethio)-2,3-di-O-methyl]- α -CD we were able to perform the most loaded nanoparticles (% of associated drug = 62) with a size of 97.9 nm. Tests of these nanoparticles on AML cells showed that they were efficient inducers of cell death, due to the encapsulated iodinin, since empty nanoparticles showed no adverse effects on the cells. Furthermore, amphiphilic α -CD derivatives could be functionalised on the secondary hydroxyl groups by targeting moieties such as folate³⁸ or by incorporating the fragment antigen-binding (Fab) of a monoclonal antibody onto CDs to target IL-3 receptor α -chain (IL-3R α , highly expressed on AML LSCs)²⁴.

Acknowledgements

Pr. Marc Le Borgne thanks Mr. Christophe Villard (Student Exchange Office of the Faculty of Pharmacy of Lyon) for his precious help. Dr. Florent Perret thanks Pr. Julien Leclaire for his financial help and Dr. Yves Chevalier from LAGEP laboratory for zeta sizer experiments. Pr. Stein O. Døskeland and Lars Herfindal thank Ing. Nina Lied Larsen for assistance with cell experiments.

Disclosure statement

No potential conflict of interest was reported by the authors.


Funding


The present work was supported by the "Partenariats Hubert Curien" (PHC) (Campus France, Programme Aurora, Grant Agreement No. 27460VC), by the Norwegian Research Council [Grant Agreement No. 213191/F11] and the Norwegian Cancer Society (Project no.: 4529447). Pr. Marc Le Borgne also thanks the


“Institut français d’Oslo” for their support via the Åsgard Programme 2010. This scientific work was also supported by financial support from Rhône-Alpes region through an Explo’ra Sup scholarship (academic year 2012–2013).


ORCID

Sylvie Radix  <http://orcid.org/0000-0002-3994-6157>

Pål Rongved  <http://orcid.org/0000-0001-6678-1952>

Stein O. Døskeland  <http://orcid.org/0000-0002-4009-4756>

Marc Le Borgne  <http://orcid.org/0000-0003-1398-075X>

Florent Perret  <http://orcid.org/0000-0003-1413-6374>

References

- Laursen JB, Nielsen J. Phenazine natural products: biosynthesis, synthetic analogues, and biological activity. *Chem Rev* 2004;104:1663–86.
- Abdelfattah MS, Ishikawa N, Karmakar UK, et al. New phenazine analogues from *Streptomyces* sp. IFM 11694 with TRAIL resistance-overcoming activities. *J Antibiot (Tokyo)* 2016;69:446–50.
- Guttenberger N, Blankenfeldt W, Breinbauer R. Recent developments in the isolation, biological function, biosynthesis, and synthesis of phenazine natural products. *Bioorg Med Chem* 2017;25:6149–66.
- Moorthy NS, Pratheepa V, Ramos MJ, et al. Fused aryl-phenazines: scaffold for the development of bioactive molecules. *Curr Drug Targets* 2014;15:681–8.
- Kumar S, Mujahid M, Verma AK. Regioselective 6-endo-dig iodocyclization: an accessible approach for iodo-benzo[a]-phenazines. *Org Biomol Chem* 2017;15:4686–96.
- Kumar S, Saunthwal RK, Mujahid M, et al. Palladium-catalyzed intramolecular Fujiwara-hydroarylation: synthesis of benzo[a]-phenazines derivatives. *J Org Chem* 2016;81:9912–23.
- Garrison AT, Abouelhassan Y, Norwood VM, 4th, et al. Structure–activity relationships of a diverse class of halogenated phenazines that targets persistent, antibiotic-tolerant bacterial biofilms and *Mycobacterium tuberculosis*. *J Med Chem* 2016;59:3808–25.
- Udumula V, Endres JL, Harper CN, et al. Simple synthesis of endophenazine G and other phenazines and their evaluation as anti-methicillin-resistant *Staphylococcus aureus* agents. *Eur J Med Chem* 2017;125:710–21.
- Xiong Z, Niu J, Liu H, et al. Synthesis and bioactivities of phenazine-1-carboxylic acid derivatives based on the modification of PCA carboxyl group. *Bioorg Med Chem Lett* 2017;27:2010–13.
- Cimmino A, Evidente A, Mathieu V, et al. Phenazines and cancer. *Nat Prod Rep* 2012;29:487–501.
- Lu Y, Yan Y, Wang L, et al. Design, facile synthesis and biological evaluations of novel pyrano[3,2-a]phenazine hybrid molecules as antitumor agents. *Eur J Med Chem* 2017;127:928–43.
- Davis JG. *Chromobacterium iodinum* (n. sp.). *Zentralbl Bakteriol Parasitenkd Infektionskr Hyg, II Abt* 1939;100:273–6.
- McIlwain H. The anti-streptococcal action of iodinin. Naphthaquinones and anthraquinones as its main natural antagonists. *Biochem J* 1943;37:265–71.
- Podojil M, Gerber NN. The biosynthesis of 1,6-phenazinediol 5,10-dioxide (iodinin) by *Brevibacterium iodinum*. *Biochemistry* 1967;6:2701–5.
- Byng GS, Turner JM. Isolation of pigmentation mutants of *Pseudomonas phenazinium*. *J Gen Microbiol* 1976;97:57–62.
- Hiroshi T, Takashi S, Masaru I, et al. Intracellular accumulation of phenazine antibiotics produced by an alkalophilic actinomycete. I. Taxonomy, isolation and identification of the phenazine antibiotics. *Agric Biol Chem* 1988;52:301–6.
- Cesková P, Zák Z, Johnson DB, et al. Formation of iodinin by a strain of *Acidithiobacillus ferrooxidans* grown on elemental sulfur. *Folia Microbiol (Praha)* 2002;47:78–80.
- Maskey PR, Li F, Qin S, et al. Chandrananimycins A approximately C: production of novel anticancer antibiotics from a marine *Actinomadura* sp. isolate M048 by variation of medium composition and growth. *J Antibiot* 2003;56:622–9.
- Myhren LE, Nygaard G, Gausdal G, et al. Iodinin (1,6-dihydroxyphenazine 5,10-dioxide) from *Streptosporangium* sp. induces apoptosis selectively in myeloid leukemia cell lines and patient cells. *Mar Drugs* 2013;11:332–49.
- Bilal M, Guo S, Iqbal HMN, et al. Engineering pseudomonas for phenazine biosynthesis, regulation, and biotechnological applications: a review. *World J Microbiol Biotechnol* 2017;33:191.
- Viktorsson EÖ, Melling Grøthe B, Aesoy R, et al. Total synthesis and antileukemic evaluations of the phenazine 5,10-dioxide natural products iodinin, myxin and their derivatives. *Bioorg Med Chem* 2017;25:2285–93.
- Sletta H, Degnes KF, Herfindal L, et al. Anti-microbial and cytotoxic 1,6-dihydroxyphenazine-5,10-dioxide (iodinin) produced by *Streptosporangium* sp. DSM 45942 isolated from the fjord sediment. *Appl Microbiol Biotechnol* 2014;98:603–10.
- Sallas F, Darcy R. Amphiphilic cyclodextrins – advances in synthesis and supramolecular chemistry. *Eur J Org Chem* 2008;2008:957–69.
- Guo J, Russell EG, Darcy R, et al. Antibody-targeted cyclodextrin-based nanoparticles for siRNA delivery in the treatment of acute myeloid leukemia: physicochemical characteristics, in vitro mechanistic studies, and ex vivo patient derived therapeutic efficacy. *Mol Pharmaceutics* 2017;14:940–52.
- Erdogar N, Varan G, Bilensoy E. Amphiphilic cyclodextrin derivatives for targeted drug delivery to tumors. *Curr Top Med Chem* 2017;17:1521–8.
- Erdogar N, Iskit AB, Eroglu H, et al. Antitumor efficacy of bacillus calmette-guerin loaded cationic nanoparticles for intravesical immunotherapy of bladder tumor induced rat model. *J Nanosci Nanotechnol* 2015;15:10156–64.
- Zuckerman JE, Gale A, Wu P, et al. siRNA delivery to the glomerular mesangium using polycationic cyclodextrin nanoparticles containing siRNA. *Nucleic Acid Ther* 2015;25:53–64.
- Ghera BB, Perret F, Baudouin A, et al. Synthesis and characterization of O-6-alkylthio- and perfluoroalkylpropanethio- α -cyclodextrins and their O-2-, O-3-methylated analogues. *New J Chem* 2007;31:1899–906.
- Bertino-Ghera B, Perret F, Fenet B, Parrot-Lopez H. Control of the regioselectivity for new fluorinated amphiphilic cyclodextrins: synthesis of di- and tetra(6-deoxy-6-alkylthio)- and 6-(perfluoroalkylpropanethio)- α -cyclodextrin derivatives. *J Org Chem* 2008;73:7317–26.
- Ghera BB, Perret F, Chevalier Y, Parrot-Lopez H. Novel nanoparticles made from amphiphilic perfluoroalkyl alpha-cyclodextrin derivatives: preparation, characterization and application to the transport of acyclovir. *Int J Pharm* 2009;375:155–62.
- Perret F, Duffour M, Chevalier Y, Parrot-Lopez H. Design, synthesis, and in vitro evaluation of new amphiphilic

- cyclodextrin-based nanoparticles for the incorporation and controlled release of acyclovir. *Eur J Pharm Biopharm* 2013;83:25–32.
32. Perret F, Marminon C, Zeinyeh W, et al. Preparation and characterization of CK2 inhibitor-loaded cyclodextrin nanoparticles for drug delivery. *Int J Pharm* 2013;441:491–8.
 33. Lacaze N, Gombaudo-Saintonge G, Lanotte M. Conditions controlling long-term proliferation of Brown Norway rat promyelocytic leukemia in vitro: primary growth stimulation by microenvironment and establishment of an autonomous Brown Norway 'leukemic stem cell line'. *Leuk Res* 1983;7:145–54.
 34. Bøe R, Gjertsen BT, Vintermyr OK, et al. The protein phosphatase inhibitor okadaic acid induces morphological changes typical of apoptosis in mammalian cells. *Exp Cell Res* 1991;195:237–46.
 35. Oftedal L, Selheim F, Wahlsten M, et al. Marine benthic cyanobacteria contain apoptosis-inducing activity synergizing with daunorubicin to kill leukemia cells, but not cardiomyocytes. *Mar Drugs* 2010;8:2659–72.
 36. Róka E, Ujhelyi Z, Deli M, et al. Evaluation of the cytotoxicity of α -cyclodextrin derivatives on the caco-2 cell line and human erythrocytes. *Molecules* 2015;20:20269–85.
 37. Gausdal G, Gjertsen BT, McCormack E. Abolition of stress-induced protein synthesis sensitizes leukemia cells to anthracycline-induced death. *Blood* 2008;111:2866–77.
 38. Erdoglar N, Esendagli G, Nielsen T, et al. From therapeutic efficacy of folate receptor-targeted amphiphilic cyclodextrin nanoparticles as a novel vehicle for paclitaxel delivery in breast cancer. *J Drug Target* 2018;26:66–74.